

Conductance Characteristics between a Normal Metal and a Superconductor Carrying a Supercurrent

Degang Zhang,¹ C. S. Ting,¹ and C.-R. Hu²

¹*Texas Center for Superconductivity and Department of Physics,
University of Houston, Houston, TX 77204, USA*

²*Department of Physics, Texas A&M University, College Station, Texas, 77843, USA*

The low-temperature conductance (G) characteristics between a normal metal and a clean superconductor (S) carrying a supercurrent I_s parallel to the interface is theoretically investigated. Increasing I_s causes lowering and broadening of (1) coherence peaks of s-wave S, and d-wave S at (100) contact, (2) midgap-states-induced zero-bias conductance peak for d-wave S at (110) contact, and (3) Andreev-reflection-induced enhancement of G within the gap near the metallic-contact limit. Novel features found include a current-induced central peak and a three-humped structure at intermediate barrier strength, etc.

PACS numbers: 74.45.+c, 74.50.+r, 74.25.Sv, 74.42.-h

It is well-known that Andreev reflection plays a fundamental role in understanding the transport properties of a normal metal/superconductor junction (NSJ) [1]. From the current-voltage (I - V), or the differential conductance [$G(V) \equiv dI(V)/dV$] characteristics of the junction, one can learn much information about S, including its elementary excitation spectrum and its order-parameter symmetry, etc. Blonder et al. have developed a general theory [2] for studying I - V and $G(V)$ of an NSJ that allows a dimensionless barrier-strength parameter z to range from metallic contact, $z = 0$, to the tunneling regime, $z \gg 1$. There only conventional s-wave symmetry for S was considered. Recently, much attention has been paid to the conductance characteristics of d-wave, cuprate S in both theory and experiment [3-13]. Due solely to the sign change of the d-wave gap-function order parameter $\Delta(\mathbf{k})$ on the Fermi surface, a zero-bias conductance peak (ZBCP) appears in the tunneling spectrum of an N/(d-wave S) junction with non-(n0m) contact [4,5,6]. The ZBCP arises from a sizable number of midgap states formed at the S side of the N/S interface and appears for all z but is narrower and taller for larger z . In a large magnetic field, the ZBCP splits into two peaks [7,8,10,11]. It is interesting to also study the effect of a supercurrent I_s in S on $G(V)$. Very recently, $G(V)$ for tunneling into a diffusive s-wave superconducting wire carrying an I_s was measured and compared with theory [14]. It was shown that the coherence peaks were suppressed and broadened with increasing I_s , and the effect is the same as that caused by a magnetic field. Because the width and thickness of the wire were smaller than the superconducting coherence length and penetration depth, all variations transverse to the wire could be neglected, as was the magnetic field generated by I_s . The positions of the coherence peaks in $G(V)$ were found to practically not shift with I_s , up to $\sim 4/5$ of the critical current. In this work, we investigate theoretically the conductance characteristics of a clean NSJ with an I_s in S parallel to the interface by extending the theory of

Blonder et al. [2]. Contrary to Ref. [14], this work is not limited to large z . We consider both s-wave and d-wave S with (100) and (110) contacts. Some novel results are obtained, especially for $z \lesssim 1$, when $G(V)$ does not simply reflect the thermally-smeared quasi-particle density of states. Hopefully, these predictions can be confirmed experimentally. Unlike Ref. [14], the present work does not consider Coulomb blockade, which is presumably not so important in an extended system and in the clean limit. As in Ref. [14], we also assume a uniform I_s , and neglect self-field.

When a uniform I_s passes through a conventional three-dimensional s-wave S, the phase of $\Delta(\mathbf{k})$ has a spatial variation of $2\mathbf{q}_s \cdot \mathbf{x}$, where $\mathbf{x}$ is the center-of-mass position of a Cooper pair, $\mathbf{q}_s = (m_*/2)\mathbf{v}_s$, with $\mathbf{v}_s$ the supercurrent velocity, and m_* the mass of a Cooper pair. ($\hbar = 1$ is assumed throughout this work.) At temperature $T = 0$, the magnitude of the order parameter Δ_q stays unchanged until the Landau criterion is satisfied (i.e. $q = 0.5\Delta^0$, where $q \equiv q_s/k_F$ and $\Delta^0 \equiv \Delta_0/E_F$). Here Δ_0 is the superconducting gap when $I_s = 0$, k_F and E_F are the Fermi momentum and energy, respectively. When $q \geq 0.5\Delta^0$, S becomes gapless, and quasi-particles are generated in a portion of the Fermi surface [15]. We shall see that this can lead to a ZBCP in $G(V)$ for an N/(s-wave S) junction with the barrier strength $z \simeq 1$. This current-induced ZBCP is always quite broad and not very tall, and its height decreases for larger z . It is therefore characteristically different from the ZBCP induced by the midgap surface states in a d-wave S with non-(n0m) contact that is narrower and taller for larger z [4]. (The midgap-states-induced ZBCP has been ubiquitously observed in high- T_c cuprate and other unconventional Ss.)

As q is increased further, Δ_q gradually decreases to zero at $q = 0.67\Delta^0$ [Fig. 1(a)]. The supercurrent density quickly reaches a peak (the thermodynamic critical current density) at $q = q_c = 0.515\Delta^0$ [Figs. 1(c)] [16].

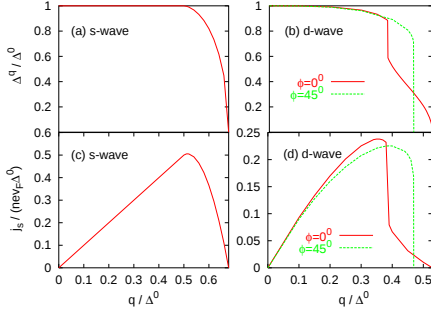


FIG. 1: Dependence of the superconducting order parameter on the normalized supercurrent-velocity parameter q for (a) an s-wave and (b) a d-wave S. (ϕ is the angle between the supercurrent and the antinodal direction in the latter case.) In (c) and (d), the corresponding dependences of supercurrent density on q are given.

The region $q > q_c$, in which I_s is a decreasing function of q , is unstable and can not be observed experimentally. (For a two-dimensional s-wave S, superconductivity disappears immediately after the Landau criterion is met. Then $q_c = 0.5\Delta^0$.)

Different from that in an s-wave S, the Δ_q -vs- q relation in a d-wave S also depends on the direction of the supercurrent. (Here Δ_q denotes the maximum gap in the presence of I_s .) For a two-dimensional d-wave S with a supercurrent, the gap-function order parameter at $T = 0$ is described by [17]

$$\pi \ln \frac{\Delta^0}{\Delta^q} = \int_{\geq} d\theta \cos^2(2\theta) \ln(g + \sqrt{g^2 - 1}), \quad (1)$$

where $g \equiv \frac{2q}{\Delta^q} \left| \frac{\cos(\theta - \phi)}{\cos(2\theta)} \right|$, $\Delta^q = \Delta_q/E_F$, ϕ is the angle between the supercurrent and the antinodal direction, and the integral in Eq. (1) is from 0 to 2π with the constraint $g^2 - 1 \geq 0$.

Figure 1(b) shows the dependence of the d-wave Δ_q on q at $\phi = 0$ and $\pi/4$. We can see that when q is less than $\sim 0.3\Delta^0$, the changes of the order parameter with q in both the antinodal and nodal directions are almost the same. However, a great difference exists for larger q . When I_s is applied along the antinodal direction, Δ^q has a sharp drop (from $0.883\Delta^0$ to $0.588\Delta^0$) between $q = 0.384\Delta^0$ and $0.385\Delta^0$. After that it drops continuously to zero at $q = 0.53\Delta^0$. When $\phi = \pi/4$, Δ^q gradually decreases to $0.689\Delta^0$ at $q = 0.469\Delta^0$, and has no solution beyond. Fig. 1(d) gives the corresponding dependences of the supercurrent density on q [17]. It is seen that the thermodynamic critical current is reached at $q = q_c = 0.35\Delta^0$ ($0.39\Delta^0$) for current in the antinodal

(nodal) direction.

The elementary excitations in S are governed by the time-independent Bogoliubov-de Gennes equations [18]:

$$Eu(\mathbf{x}) = h_0 u(\mathbf{x}) + \int d\mathbf{x}' \Delta(\mathbf{s}, \mathbf{r}) v(\mathbf{x}'), \quad (2a)$$

$$Ev(\mathbf{x}) = -h_0 v(\mathbf{x}) + \int d\mathbf{x}' \Delta^*(\mathbf{s}, \mathbf{r}) u(\mathbf{x}'), \quad (2b)$$

where $\mathbf{s} = \mathbf{x} - \mathbf{x}'$, $\mathbf{r} = \frac{1}{2}(\mathbf{x} + \mathbf{x}')$, and $h_0 = -\frac{\nabla^2}{2m} + U\delta(x) - \mu$ with μ the chemical potential. It is useful to express the superconducting order parameter in the form: $\Delta(\mathbf{s}, \mathbf{r}) = \int d\mathbf{k} e^{i\mathbf{k} \cdot \mathbf{s}} \Delta(\mathbf{k}, \mathbf{r}) e^{i2\mathbf{q}_s \cdot \mathbf{r}}$ [3]. Neglecting the proximity effect near the N/S interface at $x = 0$, we have $\Delta(\mathbf{k}, \mathbf{r}) = \Delta(\mathbf{k})\Theta(x)$, where $\Theta(x)$ is a step function, and $\Delta(\mathbf{k})$ is the order parameter of a bulk S in the presence of I_s .

In the WKB approximation, Eqs. (2) have special solutions of the form

$$\begin{pmatrix} u \\ v \end{pmatrix} = e^{i\mathbf{k}_F \cdot \mathbf{x}} \begin{pmatrix} e^{i\mathbf{q}_s \cdot \mathbf{x}} \bar{u} \\ e^{-i\mathbf{q}_s \cdot \mathbf{x}} \bar{v} \end{pmatrix}, \quad (3)$$

where $\bar{u}(\mathbf{x})$ and $\bar{v}(\mathbf{x})$ obey the generalized Andreev equations [1]:

$$(E - \frac{\mathbf{q}_s^2}{2m} - \frac{\mathbf{q}_s \cdot \mathbf{k}_F}{m}) \bar{u} = -\frac{i(\mathbf{k}_F + \mathbf{q}_s)}{m} \cdot \nabla \bar{u} + \Delta(\mathbf{k}_F) \Theta(x) \bar{v}, \quad (4a)$$

$$(E + \frac{\mathbf{q}_s^2}{2m} - \frac{\mathbf{q}_s \cdot \mathbf{k}_F}{m}) \bar{v} = \frac{i(\mathbf{k}_F - \mathbf{q}_s)}{m} \cdot \nabla \bar{v} + \Delta^*(\mathbf{k}_F) \Theta(x) \bar{u}. \quad (4b)$$

Obviously, the eigenenergy E is symmetric about $E = \mathbf{q}_s \cdot \mathbf{k}_F/m$. When $\mathbf{q}_s$ is applied parallel to the interface of the NSJ, i.e. $\mathbf{q}_s = -q_s \mathbf{e}_y$, we have

$$\begin{pmatrix} \bar{u}_\nu \\ \bar{v}_\nu \end{pmatrix} = e^{i\alpha_\nu x} \begin{pmatrix} u_\nu^> \\ v_\nu^> \end{pmatrix} \quad (\text{for } x > 0), \quad (5a)$$

$$\begin{pmatrix} \bar{u}_\nu \\ \bar{v}_\nu \end{pmatrix} = \begin{pmatrix} e^{i\beta_\nu x} u_\nu^< \\ e^{i\gamma_\nu x} v_\nu^< \end{pmatrix} \quad (\text{for } x < 0), \quad (5b)$$

where $\nu = \text{sign}(k_{Fx})$; $\alpha_\nu = [-\nu \mathbf{q}_s^2/2 + mA_\nu]/|k_{Fx}|$, with $A_\nu \equiv \sqrt{(E + q_s k_{Fy}/m)^2 - \Delta_\nu(\mathbf{k}_F) \Delta_\nu^*(\mathbf{k}_F)}$; $\beta_\nu = m\nu[-\mathbf{q}_s^2/(2m) + E + q_s k_{Fy}/m]/|k_{Fx}|$; $\gamma_\nu = -m\nu[\mathbf{q}_s^2/(2m) + E + q_s k_{Fy}/m]/|k_{Fx}|$; $u_\nu^>(<)$ and $v_\nu^>(<)$ are constants. For example, in S, we have $B_\nu \equiv u_\nu^>/v_\nu^> = \Delta_\nu(\mathbf{k}_F)/(E + q_s k_{Fy}/m - \nu A_\nu)$.

Following Ref. [2], after a tedious but straightforward calculation, we obtain the Andreev and normal reflection coefficients, $a(E)$ and $b(E)$:

$$a(E) = \frac{2q_+(k_+ + k_-)}{B_-(-k_- + q_+ + 2imU)(k_+ - q_- + 2imU) - B_+(k_+ + q_+ + 2imU)(-k_- - q_- + 2imU)}, \quad (6a)$$

$$b(E) = \frac{B_+(k_- + q_- - 2imU)(-k_+ + q_+ - 2imU) + B_-(k_+ - q_- + 2imU)(k_- + q_+ - 2imU)}{B_-(-k_- + q_+ + 2imU)(k_+ - q_- + 2imU) - B_+(k_+ + q_+ + 2imU)(-k_- - q_- + 2imU)}. \quad (6b)$$

Here $q_+ = |k_{Fx}| + \beta_+$, $q_- = |k_{Fx}| + \gamma_+$, and $k_\nu = |k_{Fx}| + \nu\alpha_\nu$. The critical supercurrent velocity is much less than the Fermi velocity. So the Andreev approxima-

tion, $q_\pm \approx k_\pm \approx |k_{Fx}|$, also holds in the presence of a supercurrent. The normalized conductance can then be calculated according to a formula given in Ref. [2]:

$$G = \frac{G_s}{G_n}, \quad G_n = -\frac{e^2}{\pi} \int_{-\infty}^{+\infty} dE \int_{-\frac{\pi}{2}}^{\frac{\pi}{2}} d\theta \frac{\partial f(E - eV)}{\partial E} [1 - |b(+\infty)|^2],$$

$$G_s = -\frac{e^2}{\pi} \int_{-\infty}^{+\infty} dE \int_{-\frac{\pi}{2}}^{\frac{\pi}{2}} d\theta \frac{\partial f(E - eV)}{\partial E} [1 + |a(-E)|^2 - |b(E)|^2], \quad (7)$$

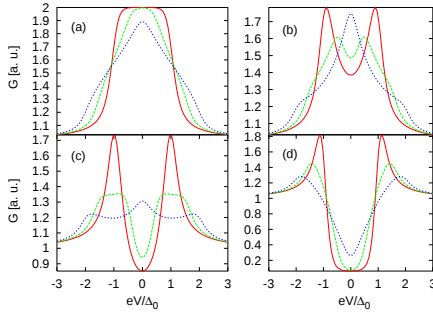


FIG. 2: The normalized differential conductance vs voltage for a normal metal/s-wave superconductor junction: (a) $z = 0$, (b) $z = 0.5$, (c) $z = 1.0$, and (d) $z = 5.0$. Red: $q = 0$, green: $q = 0.3\Delta^0$, and blue: $q = 0.515\Delta^0$, at which the thermodynamic critical current is reached. Note that $q \equiv q_s/k_F$, and $\Delta^0 \equiv \Delta_0/E_F$.

where $|k_{Fx}| = k_F \cos\theta$, $f(E)$ is the Fermi distribution function, G_n and G_s are the differential conductance for S in the normal and superconducting states, respectively.

S-wave superconductor. In this case, the superconducting order parameter $\Delta_\nu(\mathbf{k}_F) = \Delta_q$ is independent of ν .

In Fig. 2, $G(V)$ at various q and $z \equiv 2mU/k_F$ is plotted. [We have used $k_B T = 0.01E_F$ and $\Delta_0 = 0.1E_F$.] When $z = 0$ and $q = 0$, electrons incoming with all momenta $\mathbf{k}_F$ with $k_{Fx} > 0$ can enter S and equal number of holes at opposite momenta are retro-reflected into N if $|eV| < \Delta_0$. So the normalized conductance $G = 2.0$ within the superconducting gap if $T = 0$. With increasing q , the range of $G = 2.0$ diminishes and the $G(V)$ curve turns into a nearly triangular peak centered at zero bias [Fig. 2(a)]. At large z [Fig. 2(d)], the coherence peaks are suppressed and broadened with increasing q , but contrary to the case of a diffusive superconducting wire [14], here the peaks of $G(V)$ move outward while the

gap shrinks. The intermediate- z results are even richer in behavior [Figs. 2(b) and (c)]: A fairly broad and not very tall peak appears at zero bias and a three-humped structure can also appear for nearly critical q . Note that the larger is z , the lower is this current-induced ZBCP. The area under this peak is also not conserved as z changes. These features are characteristically different from the ZBCP induced by the midgap surface states in d-wave S with non-(n0m) contacts. [4]

For electrons entering an NSJ at a fixed incident angle θ , a ZBCP would result from their contributions to the normalized conductance if $2q|\sin\theta| > \Delta^0$ is satisfied. Thus, one can see this peak only if $q > 0.5\Delta^0$ is satisfied. For $0.5\Delta^0 < q < 0.67\Delta^0$, there is a critical angle $|\theta_c| = \arcsin(\Delta^0/2q)$, which decreases from 90° to 48.3° in this range. No ZBCP is induced by electrons with incident angle $|\theta| < |\theta_c|$. However, only a small portion of this regime can be observed, because only the region $q \leq 0.515\Delta^0$ is stable.

D-wave superconductor. In this case, the pair potential has the form $\Delta_\nu(\mathbf{k}_F) = \Delta_q \cos(2\theta_\nu)$. Here, $\theta_\nu = \theta + \nu\alpha$, α is the angle between the antinodal direction and the positive x axis.

Figure 3 presents the normalized conductance at different z and q for a d-wave S with (100) contact (i.e. $\alpha = 0^\circ$). For $z = 0$ [Fig. 3(a)], the central peak due to Andreev reflection is gradually suppressed and slightly broadened. For large z [Fig. 3(d)] one sees mainly the filling up of the central dip with only a slight suppression of the coherence peaks as q increases. For intermediate z [Figs. 3(b) and (c)], one sees intricate behavior with some similarity to the corresponding figures in Fig. 2.

Figure 4 shows the normalized conductance at different z and q for a d-wave S with (110) contact (i.e. $\alpha = 45^\circ$). It is seen that the ZBCP induced by the midgap surface

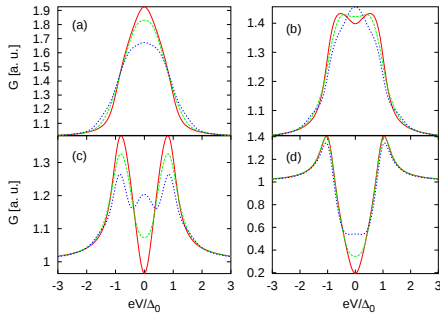


FIG. 3: The normalized differential conductance vs voltage for a normal metal/d-wave superconductor junction with (100) contact: (a) $z = 0$, (b) $z = 0.5$, (c) $z = 1.0$, and (d) $z = 5.0$. Red: $q = 0$, green: $q = 0.2\Delta^0$, and blue: $q = 0.35\Delta^0$, at which the thermodynamic critical current is reached.

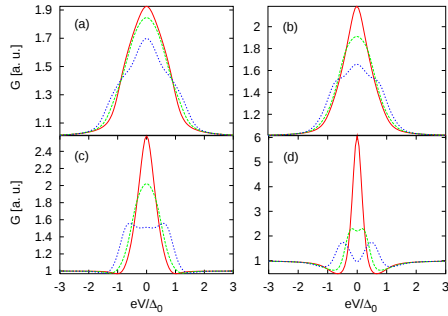


FIG. 4: The normalized differential conductance vs voltage for a normal metal/d-wave superconductor junction with (110) contact. The z values considered are the same as in Fig. 3. The q values considered are: Red: $q = 0$, green: $q = 0.2\Delta^0$, and blue: $q = 0.39\Delta^0$, at which the critical current is reached.

states is suppressed, broadened, and eventually split at sufficiently large z when q is increased.

In conclusion, we have studied the differential conductance of a clean normal metal/superconductor junction carrying a supercurrent parallel to the junction interface, for barrier strength ranging from metallic-contact to the tunneling regime. In the tunneling regime, we obtain results similar to the case of a diffusive s-wave superconducting wire studied recently, viz., suppression and broadening of the coherence peaks for both an s-wave superconductor and a d-wave superconductor with (100) contact, except that the coherence peaks are found to move outward in the s-wave case. For d-wave superconductor with (110) contact we also find the midgap-surface-states-induced ZBCP to be suppressed and broadened and eventually split with increasing supercurrent. In the metallic-contact limit, supercurrent causes the Andreev-reflection-induced conductance en-

hancement within the (maximum) gap to become weakened and broadened. For intermediate barrier strengths some novel features are revealed including a current-induced zero-bias peak and a three-humped structure near the thermodynamical critical current density. It is hoped that these predictions can be observed experimentally. We conclude with the remark that this formulation can also be applied to the case of an d+s superconductor. Because the critical current for an s-wave superconductor is larger than that for a d-wave one, the existence of an s component can be verified by a supercurrent reaching a magnitude between the critical values of the two waves.

We wish to thank J. Wei for helpful discussions. This work was supported by the Texas Center for Superconductivity and Advanced Materials at the University of Houston and by the Robert A. Welch Foundation (Ting).

-
- [1] A. F. Andreev, Zh. Eksp. Teor. Fiz. **46**, 1823 (1964) [Sov. Phys. JETP **19**, 1228 (1964)].
 - [2] G. E. Blonder, M. Tinkham, and T. M. Klapwijk, Phys. Rev. B **25**, 4515 (1982).
 - [3] Chr. Bruder, Phys. Rev. B **41**, 4017 (1990).
 - [4] C. -R. Hu, Phys. Rev. Lett. **72**, 1526 (1994).
 - [5] Y. Tanaka and S. Kashiwaya, Phys. Rev. Lett. **74**, 3451 (1995).
 - [6] J. H. Xu, J. H. Miller, Jr., and C. S. Ting, Phys. Rev. B **53**, 3604 (1996).
 - [7] M. Covington, M. Aprili, E. Paraoanu, L. H. Greene, F. Xu, J. Zhu, and C. A. Mirkin, Phys. Rev. Lett. **79**, 277 (1997).
 - [8] M. Fogelström, D. Rainer, and J. A. Sauls, Phys. Rev. Lett. **79**, 281 (1997).
 - [9] J. Y. T. Wei, N.-C. Yeh, D. F. Garrigus, and M. Strasik, Phys. Rev. Lett. **81**, 2542 (1998).
 - [10] M. Aprili, E. Badica, and L. H. Greene, Phys. Rev. Lett. **83**, 4630 (1999).
 - [11] R. Krupke and G. Deutscher, Phys. Rev. Lett. **83**, 4634 (1999).
 - [12] H. Aubin, L. H. Greene, Sha Jian, and D. G. Hinks, Phys. Rev. Lett. **89**, 177001 (2002).
 - [13] A. Kohen, G. Leibovitch, and G. Deutscher, Phys. Rev. Lett. **90**, 207005 (2003).
 - [14] A. Anthore, H. Pothier, and D. Esteve, Phys. Rev. Lett. **90**, 127001 (2003).
 - [15] A. M. Zagoskin, *Quantum Theory of Many-Body Systems: Techniques and Applications* (Springer, 1998).
 - [16] J. Bardeen, Rev. Mod. Phys. **34**, 667 (1962); K. Maki, *Gapless Superconductivity*, in *Superconductivity*, ed. by R. D. Parks (Marcer Dekker, New York, 1969).
 - [17] Degang Zhang *et al.*, to be published.
 - [18] P. G. de Gennes, *Superconductivity of Metals and Alloys* (Benjamin, New York, 1966).